AD-A254 643



OFFICE OF NAVAL RESEARCH
Contract N00014-82-0280
Task No. NR413EOOl

TECHNICAL REPORT NO. 50

Halogen Surface Chemistry on Si(100)-(2x1) by

John T. Yates, Jr., C.C. Cheng, Q. Gao, and W.J. Choyke
Submitted To

ISISS-University of Wisconsin-Milwaukee

Surface Science Center Department of Chemistry University of Pittsburgh Pittsburgh, PA 15260 SELECTE AUG3 1992

29 June-2 July 1992

Reproduction in whole or in part is permitted for any purpose of the United States Government

This document had been approved for public release and sale; its distribution is unlimited



REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 2.	GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
50		_
4. TITLE (and Subilitie)		S. TYPE OF REPORT & PERIOD COVERED
Halogen Surface Chemistry on Si(100)	-(2x1)	Preprint
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(*) John T. Yates, Jr., C.C. Cheng, Q. G W.J. Choyke	ao, and	8. CONTRACT OR GRANT NUMBER(*)
9. PERFORMING ORGANIZATION NAME AND ADDRESS Surface Science Center Department of Chemistry	PA 15260	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
University of Pittsburgh, Pittsburgh	, FA 15200	
11. CONTROLLING OFFICE NAME AND ADDRESS		12. REPORT DATE 29 June-2 July 1992
		13. NUMBER OF PAGES
14. MONITORING AGENCY NAME & ADDRESS(IL different I	rom Controlling Office)	15. SECURITY CLASS. (of this report)
		Unclassified
		154. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (31 th: 1 Report)		•
17. DISTRIBUTION STATEMENT (a) the abstract entered in	Block 20, Il different fro	m Report)
		- ···
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and	identity by block number)
silicon chlorine		
Eley Rideal		
Si-Cl bond		
atomic hydrogen		
	stry of adsorbed h	

The surface chemistry of adsorbed halogen atoms on Si(100) has been studied using several surface science methods. It has been found using electron-stimulated desorption ion angular distribution (ESDIAD) that Cl atoms bond to dangling bonds on symmetric Si₂ dimer sites, and that the Si-Cl bond angle is tilted (25°±4°) from the normal in the vertical plane containing the symmetric Si₂ dimer bond. The covalently-bonded halogens Cl, Br, and I have been studied on Si(100) using atomic hydrogen bombardment at low substrate temperatures (300 - 630 K). In all cases, facile elimination of the hydrogen halide occurs, and the coverage of halogen may be driven to zero by moderate exposure to atomic hydrogen. The halogen extraction process is almost non-activated, suggesting

DD 1 JAN 73 1473

occurs, and the coverage of halogen may be driven to zero by moderate exposure to atomic hydrogen. The halogen extraction process is almost non-activated, suggesting that the chemical reaction to produce hydrogen halide species is driven by the potential energy carried by the atomic hydrogen species. This is an example of an Eley-Rideal reaction process and provides a potentially useful new approach for controlling atomic layer chemistry on semiconductors.

E (When Date Entered)

Submitted to: ISISS-University of Wisconsin-Milwaukee

WISCOUSTII MITTWOOM

Date: 29 June-2 July, 1992

Halogen Surface Chemistry on Si(100)-(2x1)

John T. Yates, Jr., C.C. Cheng, Q. Gao, and W.J. Choyke

Surface Science Center Department of Chemistry University of Pittsburgh Pittsburgh, PA 15260

412-624-8320

DTIC QUALITY INSPECTED 3

Acce	ssion F	'or	
	GRA&I	·	To the same of the
DTIC	TAB		ñ
Unani	nounced		ñ
Just	lficati	on	
1	ibution	ty C	
	Avail		or
Dist	Spec	ial	
A-1			明

Halogen Surface Chemistry on Si(100)-(2x1)

John T. Yates, Jr., C.C. Cheng, Q. Gao, and W.J. Choyke

Surface Science Center Department of Chemistry University of Pittsburgh Pittsburgh, PA 15260

Abstract

The surface chemistry of adsorbed halogen atoms on Si(100) has been studied using several surface science methods. It has been found using electron-stimulated desorption ion angular distribution (ESDIAD) that Cl atoms bond to dangling bonds on symmetric Si2 dimer sites, and that the Si-Cl bond angle is tilted (25°±4°) from the normal in the vertical plane containing the symmetric Si2 dimer bond. The covalently-bonded halogens Cl, Br, and I have been studied on Si(100) using atomic hydrogen bombardment at low substrate temperatures (300 - 630 K). In all cases, facile elimination of the hydrogen halide occurs, and the coverage of halogen may be driven to zero by moderate exposure to atomic hydrogen. The halogen extraction process is almost non-activated, suggesting that the chemical reaction to produce hydrogen halide species is driven by the potential energy carried by the atomic hydrogen species. This is an example of an Eley-Rideal reaction process and provides a potentially useful new approach for controlling atomic layer chemistry on semiconductors.

I. Introduction

The development of low temperature surface processes to manipulate adsorbed species on semiconductor surfaces provides the basis for new etching and thin film deposition methods to produce heterostructure semiconductor devices. Our knowledge of the fundamentals governing chemistry on semiconductor surfaces is in its infancy, and mechanistic understanding of elementary semiconductor surface processes is needed[1]. In this paper, the bonding structure of Cl on Si(100) and a new class of surface reaction, involving atomic hydrogen as a reagent, are described.

II. Experimental Details

The ultrahigh vacuum apparatus and methods used for this research have been described previously[2,3]. The methods employed include temperature programmed desorption(TPD), Auger electron spectroscopy(AES), high resolution electron energy loss spectroscopy(HREELS), and digital electron-stimulated desorption ion angular distribution (ESDIAD)[4]. Halogens are adsorbed on the single crystal surface using collimated molecular beam dosers which deliver an absolutely known flux of gas, permitting quantitative exposures and uptake measurements to be made[4].

III. Results and Discussion

A. Structure of Chemisorbed Cl on Si(100)-(2 x 1)

Figure 1 shows a schematic diagram of the digital ESDIAD apparatus employed for this work[3]. An electron beam excites surface species on the Si(100) single crystal, producing beams of positive ions which are spatially detected by the microchannelplate detector system. The pattern of ion emission angles is closely related to the direction of the surface chemical bonds which are ruptured by the electronic excitation process[5]. These ion emission directions are modified by final state image and reneutralization effects[6], as well as by the electrical bias applied to the crystal for pattern compression. Corrections for all three of these effects have been made in the estimation of the Si-Cl bond angle on Si(100)-(2x1)[7,8].

Because the ion emission dynamics are governed by rapid Franck-Condon excitation from the ground state to a repulsive upper state, the statistical summation of millions of ion emission directions from an ensemble of adsorbate species on a single crystal will provide a statistical measurement of the distribution of chemical bond angles caused by thermal disorder at the measurement temperature. This permits digital ESDIAD to be used also

as a powerful tool for the study of the dynamical behavior of adsorbates[5].

Figure 2 shows a sequence of Cl⁺ ESDIAD patterns from chlorine adsorption on $Si(100)-(2 \times 1)[7,8]$. At an adsorption temperature of 120 K, a normal Cl⁺ beam is observed to overlap an underlying Cl+ pattern exhibiting two-fold symmetry. Upon annealing the chlorine-covered surface to temperatures above 120 K, the central Cl+ beam is seen to disappear, revealing the inclined beams which become more pronounced. This process culminates at about 673 K. The normal Cl+ beam is caused by a minority of adsorbed Cl atoms which bridge the symmetric Si dimer sites. These species have a high cross section for ESD production of Cl+, and the normal emission from these bridged-Cl species therefore dominates the low temperature ESDIAD pattern. As the system is heated, the bridged-Cl species convert to terminal-Cl species, with the inclined Si-Cl bonds oriented in the vertical plane which includes the [011] crystallographic axis. This azimuthal plane corresponds to the Si-Si bond directions in the Si2 surface dimers on a Si(100) terrace. The orthogonal Si-Cl beam directions correspond to inclined Si-Cl bonds on the mixture of two types of crystal terraces present on the slightly misaligned Si(100) crystal. The Si-Cl bonds are inclined 25°±4° from the normal [7,8].

Figure 3 shows the vibrational behavior of the surface as a chlorine layer is heated over the same

temperature range as used in the ESDIAD experiments[8]. 100 K, two Cl-related vibrational modes are observed at 600 cm⁻¹ and at about 300 cm⁻¹. The 600 cm⁻¹ mode is due to the Si-Cl stretching mode of the inclined Si-Cl bonds. Its frequency and intensity remains almost constant as the heating process occurs. The weak mode at about 300 cm⁻¹ is assigned to a bridging-Cl species, linked between two Si atoms in a dimer pair on the $Si(100)-(2 \times 1)$ surface. The good analogy to the vibrational frequency of bridging-Cl in compounds such as Al₂Cl₆ was employed to make this assignment[8,9]. The vibrational behavior suggests that the bridging-Cl species is a minority species, since the intensity of the 600 cm⁻¹ mode does not vary significantly during the heating process as the 300 cm⁻¹ mode decreases in intensity. The bridging-Cl species is metastable with respect to the inclined Si-Cl species, which is the most stable species on Si(100). Similar behavior was observed in the theoretical calculations of Wu and Carter[10] for F on Si(100), except that an energy barrier for the bridgeto-inclined Si-F structure was predicted to be negligible theoretically. The large change observed in the Cl+ ESDIAD pattern for the heating range 100 K - 673 K is related to the high ESD cross section for Cl+ production from the small surface coverage of bridged-Cl which exists below 673 K.

B. Facile Extraction of Chemisorbed Halogen Atoms by Atomic Hydrogen

The silicon-halogen bond may be broken easily by bombarding the surface with atomic hydrogen, produced on a hot tungsten filament in the ultrahigh vacuum system containing a low pressure of molecular hydrogen[11]. Figure 4 shows the behavior of the Cl surface coverage at a surface temperature of 300 K, along with similar measurements made for adsorbed Br and adsorbed I on Si(100). These measurements have been made in a way in which the small effect of the Auger electron beam on the halogen coverage has no effect on the interpretation. fitted curves are best fits to first-order kinetics in halogen surface coverage. It is seen that the relative rate of halogen extraction is I > Br > Cl. A similar trend has been observed in gas phase studies for the reaction of atomic hydrogen with the methyl halides to produce hydrogen halide species[12].

The bromine extraction rate was studied as a function of the pressure of H_2 used in the chamber, as seen in Figure 5. The flux of atomic hydrogen is known to be proportional to the H_2 pressure under these conditions[13]. As the hydrogen pressure is increased, the rate of Br extraction increases at a surface temperature of 430 K; the inset shows that the Br extraction rate is linearly proportional to the atomic H

flux employed. This provides direct evidence for the first-order dependence of the extraction rate on the atomic H flux.

The temperature dependence of the atomic-H induced extraction of bromine was measured as shown in Figure 6. An activation energy for this process of only 1.6 ± 0.2 kcal/mol was measured over the range $300~\mathrm{K}-630~\mathrm{K}$, as shown in the inset to Figure 6. Similar studies of the kinetics of extraction of adsorbed Cl gave an activation energy of 2.1 ± 0.2 kcal/mol for Cl/Si(100). These low activation energies are indicative that the thermal excitation of the surface species is of little importance in governing the rate of the halogen extraction process.

Considered together, the kinetic behavior of the halogen extraction process induced by atomic hydrogen corresponds to the well known, but infrequently observed, Eley-Rideal kinetic process[11]. The process involves the use of the potential energy carried by the atomic H to produce the active complex involved in the removal of surface halogen. An active complex, Si...X...H is produced when atomic H collides with the covalently-bonded halogen atom, X. Accomodation of the incoming H atom by the silicon surface is not required in this mechanism. The potential energy of the atomic hydrogen is 52 kcal/mol compared to 1/2 H₂(g), and this energy is the primary driver for the halogen extraction process observed. Such a process, occuring at low surface temperatures, could be

of significance in a variety of semiconductor technologies.

The Eley-Rideal process observed for atomic hydrogen as a reagent is potentially important for a wide range of surface chemistry. Other gas phase free radical species may be expected to be active in similar extraction processes on surfaces, and we will have to await future experiments before knowing the full implications of these first observations involving the most simple free radical species, atomic hydrogen. In particular, the use of atomic hydrogen extraction procedures for removal of surface halogen ligands (present in atomic layer epitaxy processes involving monolayers of group IV halide species) is expected to be of importance.

IV. Summary

This is a brief review of the bonding structure of chlorine on Si(100)-(2x1) and use of atomic hydrogen as a reagent for inducing halogen extraction reactions on silicon.

1. The Si-Cl bonds are inclined 25°±4° from the normal in a perpendicular plane parallel to the Si-Si bonds in the (2x1) reconstruction of Si(100). 2. It has been shown that covalently-bonded halogen atoms may be efficiently removed from Si(100) by atomic hydrogen via an Eley-Rideal process yielding volatile hydrogen halide species. The rate of the Eley-Rideal process is almost temperature independent, indicating that thermal activation from the substrate is of little importance compared to the activation induced by the potential energy of the incident atomic hydrogen itself.

V. Acknowledgement

We thank the Office of Naval Research for full support of this work.

VI. References

- [1] M.E. Gross, J.M. Jasinski and J.T. Yates, Jr., Eds.,

 "Chemical Perspectives of Microelectronic Materials,"


 Vol. 131, Materials Research Society Symposium

 Proceedings, 1989.
- [2] C.C. Cheng, R.M. Wallace, P.A. Taylor, W.J. Choyke and J.T. Yates, Jr., J. Appl. Phys., <u>67</u>, 3693 (1990).
- [3] M.J. Bozack, L. Muehlhoff, J.N. Russell, Jr., W.J. Choyke and J.T. Yates, Jr., J. Vac. Sci. Technol., A5, 1 (1987).
- [4] J.T. Yates, Jr. M.D. Alvey, K.W. Kolasinski and M.J. Dresser, Nuclear Instrumentation and Methods in Physics Research, <u>B27</u>, 147 (1987).
- [5] a) J.T. Yates, Jr., M.D. Alvey, M.J. Dresser, M.A. Henderson, M. Kiskinova, R.D. Ramsier and Z. Szabó, Science, <u>255</u>, 1397 (1992); b) R.D. Ramsier and J.T. Yates, Jr., Surf. Sci. Reports, <u>12</u>, 243 (1991).
- [6] a) Z. Miskovic, J. Vulkanic and T.E. Madey, Surf. Sci., <u>141</u>, 285 (1984); b) Z. Miskovic, J. Vulkanic and T.E. Madey, Surf. Sci., <u>169</u>, 405 (1986).
- [7] C.C. Cheng, Q. Gao, W.J. Choyke and J.T. Yates, Jr., submitted to Phys. Rev. B.
- [8] Q. Gao, C.C. Cheng, P.J. Chen, W.J. Choyke and J.T. Yates, Jr., submitted to J. Chem. Phys.

- [9] E. Maslowsky, "Vibrational Spectra for Organometallic Compounds," John Wiley and Sons, Inc., 1977, New York, p. 61.
- [10] a) C.J. Wu and E. Carter, J. Amer. Chem. Soc., 113,
 9J61 (1991); b) C.J. Wu and E. Carter, Phys. Rev. B
 45, 9065 (1992); c) P.C. Weakliem, C.J. Wu and E.
 Carter, Phys. Rev. Lett., in press.
- [11] C.C. Cheng, S.R. Lucas, H. Gutleben, W.J. Choyke and J.T. Yates, Jr., J. Amer. Chem. Soc., <u>114</u>, 1249 (1992).
- [12] a) W.E. Jones and J.L. Ma, Can. J. Chem., 64, 2192
 (1986); b) A.A. Westenberg and N. deHaas, J. Chem.
 Phys., 62, 3321 (1975).
- [13] a) D. Brennen and P.C. Fletcher, Proc. Roy. Soc.
 London, Ser. A, 250, 389 (1959); b) J.N. Smith, Jr.
 and W. Fite, J. Chem. Phys., 37, 898 (1962).

Figure Captions


- Figure 1. Digital ESDIAD apparatus for imaging chemical bond directions in adsorbed species.
- Figure 2. ESDIAD patterns of Cl⁺ from Si(100) as a function of annealing temperature. The initial Cl coverage is near 1 monolayer.
- Figure 3. HREELS study of the spectral changes as a function of annealing temperature for Cl/Si(100).
- Figure 4. Atomic hydrogen extraction for halogen adsorbates from Si(100).
- Figure 5. Hydrogen pressure dependence of Br extraction rate from Si(100).
- Figure 6. Temperature dependence of Br extraction rate from Si(100).

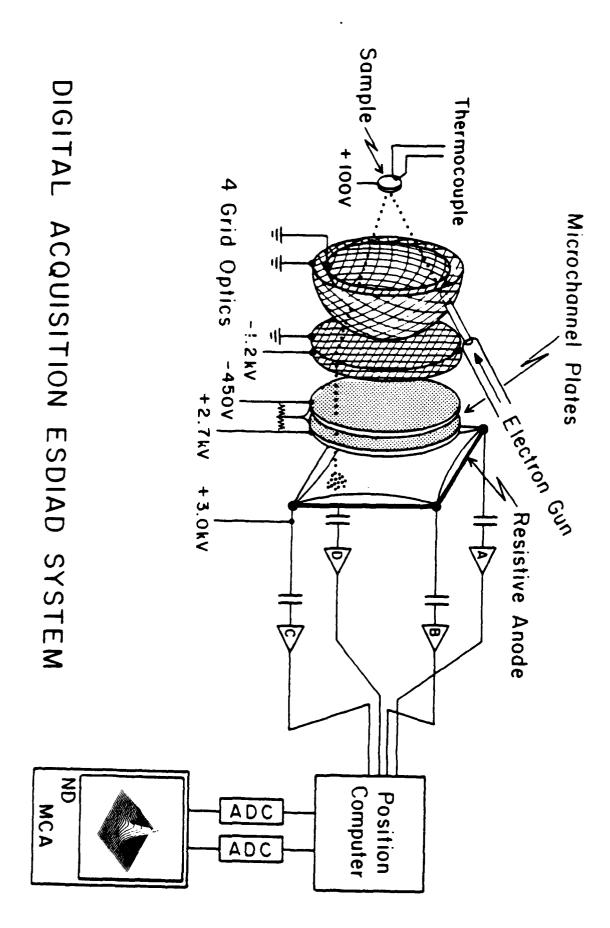


Yates, et al. Figure l


ESDIAD Patterns of Cl on Si(100)


(a) T = 120 K

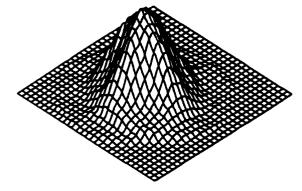

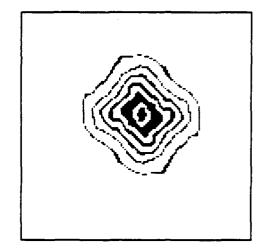



(b) $T_{anneal} = 423K$

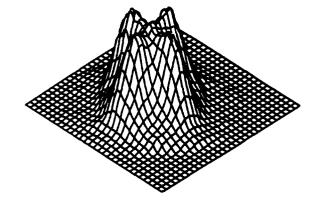

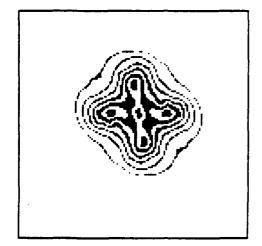

(c) $T_{anneal} = 673 \text{ K}$

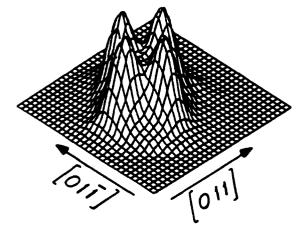


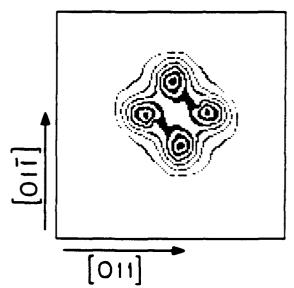


Yates, et al. Figure 2


HREELS Study of Spectral Changes

During Annealing—CI/Si(100)—(2x1)

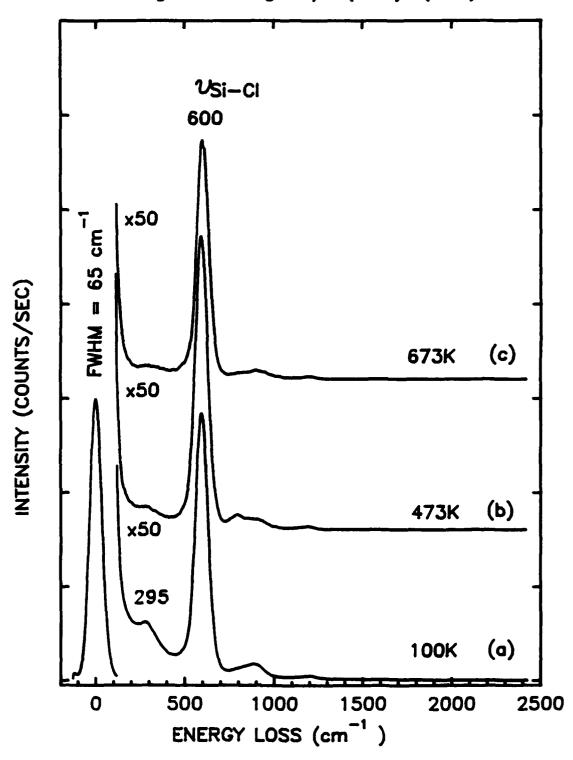


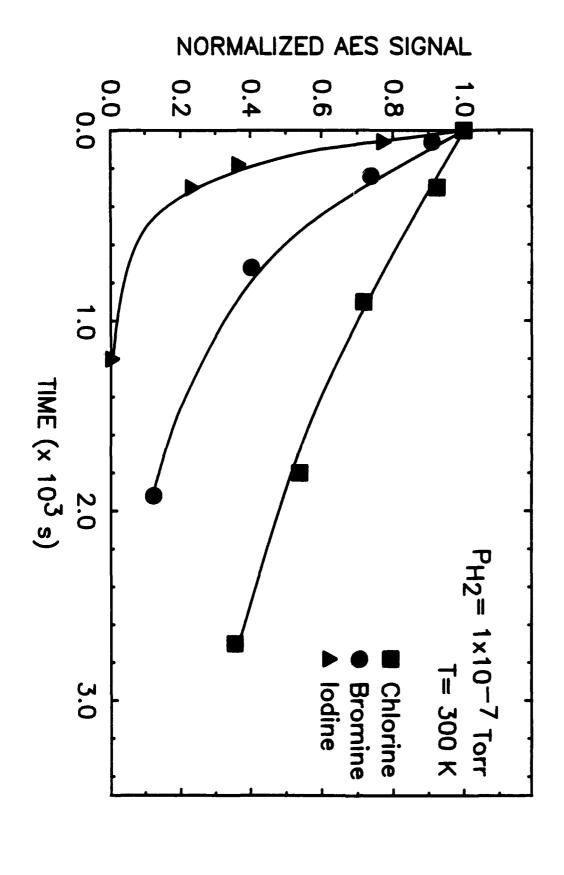

HYDROGEN PRESSURE DEPENDENCE OF Br EXTRACTION RATE

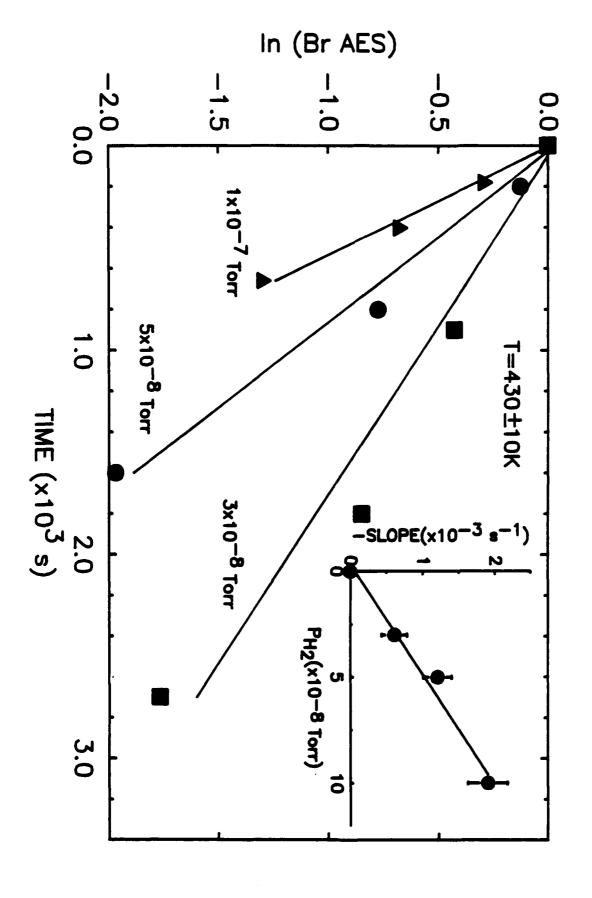

TEMPERATURE DEPENDENCE OF BROMINE EXTRACTION FROM Si(100)

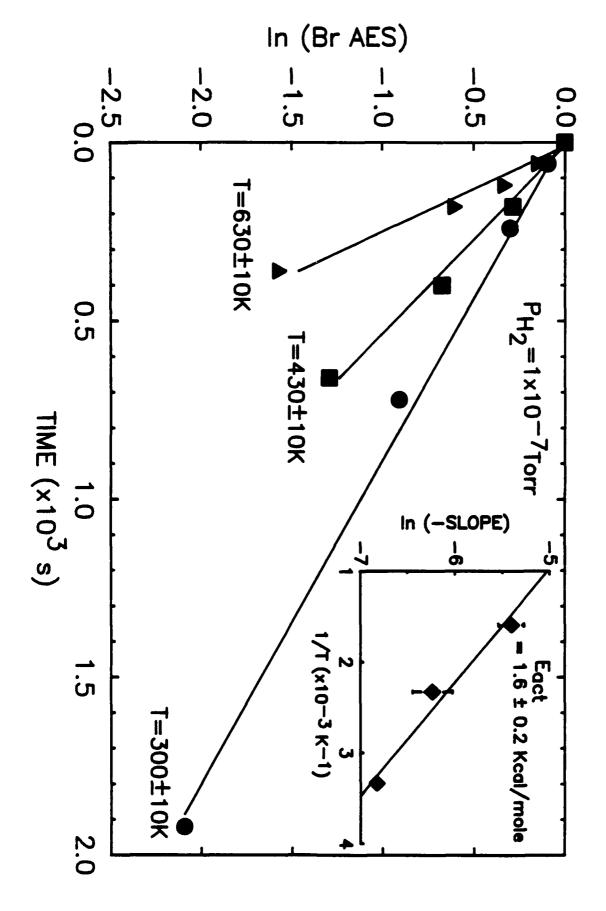

Yates, et al. Figure 6

ALE Contractor Distribution List	# Copies
D.T.I.C. Bldg # 5, Cameron Station Alexandria, VA 22314	12
Dr. Andrew Freedman Aerodyne Research, Inc. 45 Manning Road Billerica, MA 01821 Tel: (508) 663-9500 FAX: (508) 663-4918	1
e-mail: aerodyn@mitvma.mit.edu	1
Dr. Asif Kahn APA Optics 2950 NE 34th Lane Blaine, MN 55434 Tel: (612) 784-4995 FAX: (612) 784-2038 e-mail: 70702.2032@compuserve.com	_
Dr. Duncan Brown Advanced Technology Materials, Inc 7 Commerce Drive Danbury, CT 06810 Tel: (203) 794-1100 FAX: (203) 792-8040	1
Dr. Peter Norris EMCORE Corp. 35 Elizabeth Ave. Somerset, NJ 08873 Tel: (201) 271-9090	1
Prof. Joe Greene Dept. of Materials Science and Engineering University of Illinois 1101 W. Springfield Ave. Urbana, IL 61801 Tel: (217) 333-0747	1
Dr. T. P. Smith IBM T.J. Watson Research Center P. O. Box 218, Route 134 Yorktown Heights, NY 10598 e-mail: trey@ibm.com	1
Prof. Robert F. Davis N.C.S.U. Box 7907	1

Raleigh, NC 27695-7907 Tel: (919) 515-2377/3272 FAX: (919) 515-3419 e-mail: davis@mce.ncsu.edu	
Prof. Salah Bedair Department of Electrical Engineering N.C.S.U.; Box Raleigh, NC 27695 Tel: (919) 515-2336 e-mail: jll@@ecegrad.ncsu.edu	1
Max N. Yoder ONR Code 1114 Arlington, VA 22217 Tel: (703) 696-4218 FAXes (703) 696-2611/3945/5383 e-mail: yoder@charm.isi.edu	1
Dr. A. M. Goodman ONR, Code 1114 Arlington, VA 22217 Tel: (703) 696-4218 FAXes (703) 696-2611/3945/5383 e-mail: goodman@ocnr-hq.navy.mil	1
Dr. J. Pazik ONR Code 1113 Arlington, VA 22217 Tel: (703) 696-4410 FAXes (703) 696-2611/3945/5383 e-mail: pazik@ocnr-hq.navy.mil pazik@estd.decnet@ccfinrl.navy.mil	1
Prof. J. T. Yates, Jr. Dept. of Chemistry Surface Science Ctr. University of Pittsburgh Pittsburgh, PA 15260 Tel: (412) 624-8320 FAX: (412) 624-8552 e-mail: yates@vms.cis.pitt.edu	
Robert J. Markunas, R.A. Rudder Research Triangle Institute; Box 12194 Research Triangle Park, NC 27709-2194 Tel: (919) 541-6153 FAX: (919) 541-6515 e-mail: rjmk@rti.rti.org	1
Professor Mark P. D'Evelyn William Marsh Rice University Dept. of Chemistry P.O. Box 1892 Houston, TX 77251 Tel: (713) 527-8101, ext. 3468 FAX: (713) 285-5155 e-mail: mpdev@@langmuir.rice.edu	1
Dr. Howard K. Schmidt Schmidt Instruments, Inc. 2476 Bolsover, Suite 234 Houston, TX 770054 Tel: (713) 529-9040	

K: (713) 529-1147 mail: hksionwk@ricevml.rice.edu of. A. F. Tasch pt. of Electrical Engr. & Computer Science jineering Science Bldg. iversity of Texas at Austin stin, TX 78712 1: K: nail: tasch@roz.ece.utexas.edu 1 of. Charles Tu pt of Electrical & Computer Engr. SD Jolla, CA 1: (619) 534-4687 K: (619) 534-2486 mail: cwt@celece.ucsd.edu 1 of. John E. Crowell partment of Chemistry iversity of California at San Diego Jolla, CA 1: (619) 534-5441 X: (619) 534-0058 ail: jcrowell@ucsd.edu of. P. Daniel Dapkus iversity of Southern California iversity Park s Angeles, CA 90089-1147 mail: dapkus@mizar.usc.edu 1: (213) 740-4414 X: (213) 740-8684

less you are a small business invoking your 2 year proprietory ghts clause, you MUST state on the front page of your report: proved for Public Release; distribution unlimited.